

# Asian Resonance

## The Metamorphic Evolution of the Base Metal Sulphide Deposit of Rampura-Agucha, Rajasthan: Petrographical Evidences

### Abstract

Located adjacent to the Banded Gneissic Complex, Rampura-Agucha is the only sulphide ore deposit discovered within Precambrian basement gneisses of Rajasthan. The deposit is the largest Pb--Zn deposit in the country producing  $9 \times 10^5$  tons per annum. The main ore minerals are sphalerite, pyrrhotite, galena and graphite. The deposit occurs in a doubly plunging synformal structure and in a transverse section it appears as a slab that wedges out towards the bottom. The ores are metamorphosed along with the graphite-bearing metapelitic host rocks. Petrographical study of the ores and the silicates reveal that ores, silicates and ore-silicates together recorded the imprints of metamorphism and deformation and document it without undergoing resetting by later geological processes.

**Keywords:** Sulphide Ores, Basement Gneiss, Metamorphism, Deformation, Petrographical Evidences.

### Introduction

The Rampura-Agucha lead-zinc deposit (Fig.1) is located 15 km southeast of Gulabpura in the Bhilwara district, Rajasthan. The deposit is significant because of its large potential and geological setting. The deposit is the largest Pb-Zn deposit in the country (Gandhi, 2003). Rampura-Agucha base metal sulphide deposit (Fig.1) is metamorphosed along with host rock that is graphite bearing metapelitic rocks.

Metamorphism and deformation of sulphide deposits is a subject that evoked all along a great deal of scientific interest. The aim of study is to find how did the sulphide ores behave during metamorphism? What are the records of metamorphism of ores preserved? Or do the ores totally reset themselves to the later retrograde phase of metamorphism? And also how the ores equilibrated with the silicates? Are new minerals formed due to the ore-silicate equilibration? Is there any change in the chemistry of the silicates? Is there any change in the composition of the ores? Is it possible to distinguish the prograde phase and retrograde phase of metamorphism from ore-silicate textures as well as the changes underwent due to successive phases of metamorphism?

The ores vis-à-vis the silicates of Rampura—Agucha deposit have recorded the imprints of prograde phase of metamorphism and document the events of metamorphism through textural evidences. Sulphides are non-quechable; rarely do the sulphide ores preserve the imprints of earlier phases of metamorphism and easily readjust them to the later retrograde phase. This deposit is one of those rare metamorphosed sulphide deposits that occurs in Mewar gneiss and has preserved the evidences of metamorphism without being altered by later geological processes.

The deposit has drawn the attention of many workers. Deb (Deb and Sarkar, 1990) studied the deposit with the detailed REE geochemical analysis. Deb (Deb et.al, 1990B) concluded that the REE patterns of the metasediments are suggestive of continental (BGC) derivation of the sediments. Deb (Deb and Sehgal, 1997) had studied in detail the metamorphism of ores vis-à-vis the silicates and calibrated the metamorphic pressure and temperature from silicate assemblages. Holler (Holler et al., 1996) studied the fluid composition of the ores with the aid of microspectrometry. Roy (Roy et al., 1981) got into the structural aspects of the deposit and concluded that the rocks underwent multiple phases of deformations. Gandhi (Gandhi et al., 1984) suggested that the deposit



**Prabal Kr. Chattopadhyay**

Assistant Professor,  
Deptt. of Geology,  
Durgapur Govt. College,  
Durgapur, Paschim Bardhaman,  
West Bengal, India

E: ISSN No. 2349-9443

occurred in a deformed synformal structure. The model Pb-age of the deposit is 1800 Ma (Deb et al. 1989). Absence of coherent element dispersion halo around the ore orebody led some workers to suggest that the ore body was allochthonous in origin (Shah, 2004). But origin of such a huge deposit by allochthonous origin is difficult to explain. Viswanath et al (2006) studied the geometallurgical aspects of the deposit and identified the domains within the deposit with similar textural characteristics and their correlation with actual plant performance. Hazaika et al (2013) made a comparative study of geochronology of metamorphism of Rampura-Agucha deposit and Rajpura-Dariba deposit of Aravalli-Delhi belt, India. He concluded that Rampura-Agucha deposit suffered metamorphism during 1.65 Ga and again in 1.0 Ga. Misra and Bernhardt (2009) studied the metamorphism of the silicates as well as the sulfides and tried to make a comparative study of their recorded history of metamorphism.

The samples were collected from the country rock at a distance from the ore body. The samples of host rocks and ores were collected from the ore-mine and from the mine-dump. Excluding the samples of the country rocks altogether fortyeight (48) samples of host-rocks and ores were collected. Fifteen (15) samples were collected from the mine and the rest thirtythree (33) were collected from mine-dump.

Thin section slides and polish section blocks of different samples were made out in the department. Etching methods were administered to study the ore petrography in intricate detail. Different etchants were applied for different ore minerals through trial and error methods. Etchants such as thio-urea, dilute hydrochloric acid, dilute and concentrated chromic acid concentrated nitric acid were applied. However, most successful was the application of chromic acid, both dilute and concentrated. Photomicrographs were taken in the department by the camera; model 'NIKON ECLIPSE E200MV POLE'.

### Regional Geology

Rampura-Agucha deposit falls on Bhilwara supergroup vis-à-vis mineralized supracrustal Belts consists of Jahajpur Sawar, Pur-Banera, Rajpura-Dariba, Rampura-Agucha and Bhinder deposits (Fig. 2). The Bhindwara litho-tectonic belt lies between the banded gneissic complex in the west and Vindhyan supergroup to the east consists of several subparallel and sub-linear zones of differently metamorphosed sedimentary (volcanic) rocks, the metamorphism increasing from east towards the west. It is 200km in length. It is about 100km at its widest in the northern part, narrowing down to about 10km in the south, near Bhinder.

Several ore deposits, ore belts occur within the Bhilwara belt, including Rampura-Agucha deposit. The mineralisations are associated with the supracrustal rocks that were deposited on the continental rifts (Deb and Sarkar, 1990; Sinha-Roy, 1984). According to Roy (Roy et al. 1981) and Deb (Deb and Sarkar, 1990) these supracrustals are time equivalents of the Aravalli sediments (supergroup). However Rao (Raja Rao, 1970) and his co-workers (Rao et al. 1976) suggested an older age of the

# Asian Resonance

supracrustal rocks of the Bhilwara belt. Gupta (Gupta et al. 1997) included the mineralized belt under the youngest unit of Pre-Aravalli equivalent isolated cover sequences deposited in pull-apart basins within Mangalwar complex. Aravalli Craton is broadly divided into the following categories according to Ramakrishnan and Vaidyanathan (2008) (Fig. 3):

1. Archaean Mewar Gneiss.
2. Bhilwara SuperGroup-Mineralised supracrustal belts (Rampura-Agucha, Rajpura-Dariba etc.)
3. Mineralised supracrustal belts (Rampur-Agucha, Rajpura-Dariba etc.)
4. Aravalli-Delhi orogen

Mewar gneiss forms the basement of Aravalli supergroup, It consists of migmatites, gneisses and granitoids. Heron (1953) termed them as Banded Gneissic Complex (BGC). Extensive mapping by the Geological Survey of India (Gupta et al., 1980) led to the division of BGC, renamed as Bhilwara SuperGroup into three tectono-stratigraphic units viz. 1) Hindoli Group at the bottom, 2) Mangalwar complex with isolated mineralized belts at middle and 3) Sandmata complex at the top. The Rampura-Agucha belt located close to Delwara lineament at the contact of Mangalwar and Sandmata complexes to the west of Sawar belt.

### The orebody, the Ores and Their Metamorphism

#### The orebody

The Rampura—Agucha deposit explored by State Department of Geology and Mines. Geological Survey of India and HZL is one of the most important Zn—Pb—(Cu) deposit in India producing  $9 \times 10^5$  tons per annum. Total ore reserve is 63.7 mt (proven 39.2mt + probable 13.8 mt + possible 10.7 mt) with an average grade of 13.6% Zn, 1.9% Pb and 45ppm Ag (HZL, 1992), quoted by Holler (Holler and Gandhi, 1995).

The rock types in and around RA deposit, proceeding east to west (Fig. 4) are 1) Garnet—Biotite—Sillimanite—Gneiss (GBSG) with bands of amphibolite and calc-silicate rocks, intruded by aplite and pegmatite. 2) Graphite—Mica—Sillimanite schist containing the ores. 3) GBSG with lenses of amphibolites, quartzo-felspathic bands and calc-silicate rocks intruded by pegmatite aplite veins. 4) granite gneiss. 5) banded gneiss. Using garnet—biotite and garnet—hornblende geothermometers and garnet—plagioclase-sillimanite-quartz geobarometer, Deb (Deb and Sehgal, 1997) determined the  $T_{max}$  and  $P_{max}$  of metamorphism to be  $650^{\circ}C$  and 6Kb respectively. Almost all the rocks in and around the deposit contain garnet. Mg-enrichment of the silicates in the ore zone that is characteristic of metamorphosed sulfide deposit is also present here. The deposit occurs in a doubly plunging synformal structure (Gandhi et al., 1984) and in a transverse section it appears as a slab, which wedges out towards the bottom (Fig. 5). Bhatnagar (Bhatnagar and Mathur, 1989) and Roy (Roy et al., 1981) concluded that three successive phases of deformation took place in the belt. The first phase produced NNW-SSE trending isoclinal, reclined folds (F1), while the 2<sup>nd</sup> phase also produced isoclinal to

E: ISSN No. 2349-9443

tight folds and trending NE-SW, the third phase of deformation was weak.

### The Ores

The main ore minerals i.e. opaque phases in the ores are sphalerite, pyrrhotite, pyrite, galena and graphite. Minor phases include chalcopyrite, arsenopyrite and tetrahedrite—tenantite. Sphalerite dominates over other sulphides (Deb and Sarkar 1990; Ranawat et al., 1988; Genkin and Schimdt, 1991; Holler and Gandhi, 1995; Holler and Stumpf, 1995; Mukherjee et al., 1991). The gangue minerals comprise quartz, feldspar, sillimanite, graphite and phyllosilicates. Sulfosalt has also been reported as trace phases from the deposit. In lump ores the grain sizes vary widely, the largest grains could be several mm in size. Overall fabric of the ore in hand specimen is schistose.

There are numerous roundish to elliptical rock fragments within the ore, the size of these bodies range from <1mm to few cm in diameter (fig. 6). These bodies may consist of feldspar, sillimanite, graphite, phyllosilicates and quartz. Many minute bodies may consist of a single mineral or two. Here the ball structure is constituted of plagioclase feldspar and phyllosilicate. This is 'ball' or 'knead' 'durchbewegung structure' described from many ore deposits around the world (Geizer, 1971; Vokes, 1973; Sarkar et al., 1980).

Although some of the above workers differed in details, the overall explanation is that when sulphidic (Pb-Zn-Cu-Fe- sulphides) ores interlayered interwoven with silicate rocks, quartz veins are subjected to shearing during dynamo-thermal perturbations, the sulphide will generally behave as a ductile material and the silicate will yield by brittle deformation. With continual movement, the fragments of the rigid members will be rolling (may be also broken into smaller pieces), ultimately shaping into roundish bodies in a sulphidic matrix. Sometimes even phyllosilicate patches may roll into sigmoidal to rounded bodies.

### The Ores and Its Metamorphism

A moderately rich ore under the microscope may be virtually monomineralic particularly sphalerite (Fig. 7) or dominantly sphaleritic with a little or another phase such as pyrrhotite (Fig.8). There are situations where other phases such as pyrite, galena also are present in considerable proportions. Sphalerite can even be locally unimportant. In polished section with considerable proportions of silicate gangue minerals, the silicates may be shattered (Fig.7) with the sulphides having penetrated along the fractures (Fig.9) or the specimen may represent a domain where the ore is virtually strain free. Evidence of late high unmitigated strain may of course be conspicuous in virtually gang free sulphidic aggregates.

In low strain domain the overall fabric is one of annealing with the major phase polygonised and the minor phases occupying triple points. In (Fig.10) sphalerite is polygonised and pyrrhotite occupied the triple point or interstices of sphalerite.

# Asian Resonance

Speaking exclusively of the sphalerite fabric, its grain size vary widely within the limits of single photomicrograph (Fig.10) controlled by deformational recrystallisation constraints. Twinning is a common feature in Rampura—Agucha sphalerite ores. They are both growth (annealing) and deformational in type, distinguished mainly on the morphology of the twin lamellae. Sphalerite deforms at all temperatures by twinning and slip on (111) and (112-) (Clark et al., 1973). The interesting feature is the presence of small sphalerite grains within the porphyroblast of the same mineral. The guest and the host are only partially coherent, or are apparent under the microscope. Is it a result of fast growth?

Pyrrhotite and sphalerite grains show their relative strength under deformational constraints (Fig.10). Often Small droplets of pyrrhotite grains are included within the sphalerite. Symplectitic texture between sphalerite and pyrrhotite are not uncommon. It also shows their relative characters to negotiate during deformation. The aggregates of the pyrrhotite commonly show equilibrium texture with 120° angle with interstices occupied by sphalerite. The grains are virtually strain free and may be crystallized during retrogression.

Graphite is present rarely though in the ores as distorted sheaves of flakes (Fig.11). It also occurs with other silicate mineral forming ball structures (Fig. 6).

Pyrite grains are framboidal and often replaced either by sphalerite or pyrrhotite.

Chalcopyrite may show partial polygonisation and growth (annealing) twin and deformational twins. Chalcopyrite as small mineral grains occurs at the triple points in a sphalerite matrix.

Galena shows advanced recovery and recrystallisation and is included and replaced by sphalerite. This is in consonance with the available result of experimental studies. Clarke (Clark et al., 1977) showed that galena developed recovery and annealing features at temperature in which sphalerite and chalcopyrite will little response. In contrast to sphalerite, deformation twins are absent in galena as in most of the galena bearing deposits. It may be worthwhile to recall that Lyall (Lyall et al., 1986) studied the development of deformation twins in galena at various strain rates. His conclusion was that, natural deformation twinning in galena developed only at very high strain rate is not normally expected in normal situation. Therefore twinning is not normally expected to be an active deformation mechanism in galena under normal tectonic evolution. It was noticed in Rampura—Agucha ores either.

Textural relationship of the ore minerals with the silicates are equally interesting and as we shall see later, important in the interpretation of the evolution of the ores.

First of all we refer to the occurrence of sphalerite within and at the interstices of feldspar and quartz grains (Fig.12) suggesting that sphalerite coexisted with these minerals. This holds good also for the inclusion of sphalerite and pyrrhotite within

E: ISSN No. 2349-9443

feldspar and cordierite. In some cases polygonised strained quartz grains include sphalerite within them. Blebs and droplets of sphalerite and pyrrhotite are included in plagioclase feldspar. Minute blebs of elongated sphalerite and pyrrhotite grains are included within prograde biotite grains and oriented parallel to the foliation along with biotite grain (Fig. 13). No hydrous or secondary mineral is seen nearby. Ball structure observed in lump-specimen and discussed earlier are common in the ores viewed under the microscope. There this could be monomineralic being formed of such minerals as cordierite, biotite, garnet (Fig. 6) or aggregates of all these (and other) phases. Another feature is the intricate network structure of silicates and ore minerals. Occurrences of ore minerals along the cleavages of biotite grains are common. The protomylonitic quartz grains and minute grains of ore minerals are oriented parallel to the direction of dynamic deformation. Often the silicate grains are broken apart or kinked within sulphide matrix may be owing to difference in rheologic property between the two. The pyrrhotite grains are elongated and parallel to foliation along with silicate grains and are a common feature (Fig.14).

Veinlets of ore into individual silicate grains and their aggregation constitute another interesting feature under the microscope. (Fig. 9) shows a transmitted light picture of sphalerite rich sulphidic veinlet in a plagioclase feldspar aggregates. Such veinlets in incident light microscope show that they are recrystallised ore minerals. They are likely to have been emplaced by plastic flowage during a tectonothermal event. This is a case of dynamic recrystallisation. However very thin veinlets controlled by micro-fractures in individual minerals, formed by secondary hydrothermal fluids generated during retrogression could be precipitant.

#### Conclusion

Conclusion of the ore petrographic studies discussed so far are, that the ores were metamorphosed followed by recrystallisation in varying degrees. Large scale remobilization of ores during metamorphism is not evidenced except in the case of veinlets in the cleavages and fractures in the associated silicates.

#### Acknowledgement

The author is obliged to Durgapur Govt. College for providing all the necessary support to carry out the work. The author is indebted to Prof S.C. Sarkar for his constructive suggestions.

#### References

- Bhatnagar, S.N., Mathur, S. B. (1989) *Geology of Lead-Zinc Resources. HINDZINC TECH.*, Vol 1--2, pp 15—28.
- Clark, B. R., Kelly, W.C., (1973) *Sulphide Deformation studies: I. Experimental Deformation of Pyrrhotite and Sphalerite to 2000 Bars and 500°C. Economic Geology*, Vol 68, pp 332—352.
- Clark, B. R., Price, F. R., Kelly, W. C. (1977) *Effects of Annealing on Deformation Textures in Galena. Contrib. Mineral. Petrol.*, Vol 64, pp 149—165.

# Asian Resonance

- Deb, M., Bhattacharya, A.K. (1980) *Geological Setting and Conditions of Metamorphism of Rajpura-Dariba Polymetallic Ore Deposit, Rajasthan. India. Proc. 5th Quad. IAGOD Symp. E. Schweiz: Verlag, Stuttgart*, pp 679—697.
- Deb, M., Sarkar, S.C. (1990) *Proterozoic Tectonic Evolution Plus Metallogenesis in the Aravalli—Delhi Orogenic Belt, NW India. Precambrian Research*, Vol 46, pp 115—137.
- Deb, M., Sehgal, U. (1997) *Petrology and Geothermobarometry and C—O—H—S Fluid Compositions in the Environs of Rampura—Agucha Zn(-Pb) Ore Deposit, Bhilwara District, Rajasthan. Proc. Ind. Acad. Sci. (EPS)*, Vol 106, pp 343—356.
- Deb, M., Thorpe, R. I., Cumming, G. L., Wagner, P. A. (1989) *Age, Source and Stratigraphic Implications of Lead Isotope Data for Conformable Sediment- Hosted Base Metal Deposits in the Proterozoic Aravalli-Delhi Orogenic belt, NW India. Precambrian Research*, Vol 43, pp 1—22.
- Gandhi, S. M. (2003) *Rampura—Agucha Zinc-Lead deposit. Geol. Soc. India Mem.*, Vol 55, pp 154.
- Gandhi, S.M., Paliwal, H. V., Bhatnagar, S.N. (1984) *Geology and Ore Reserve Estimates of Rampura—Agucha Lead-Zinc deposit, Bhiwara District, Rajasthan. Journal of Geological Society of India*, Vol 25, pp 689-705.
- Geizer, P. (1971) *Sulphidic 'Ball Ores' and Pebble Dykes. Sveriges Geol. Undersok, C.*, Vol 662: 1—29.
- Genkin, A.D., Schmidt, S.M. (1991) *Preliminary Data of a New Thallium Minerals from the Lead-Zinc Ore Deposit. Agucha, India. News Jb. Mineral, Monatsh.*, pp 256—258.
- Gupta, S.N., Arora, S.N., Mathur, R.K., Iqbaluddin, Prasad, B., Sahai, T.N. and Sharma, S.B. (1980): *Lithostratigraphic Map of Aravalli Region, Geol. Surv. India, Calcutta.*
- Gupta, S. N., Arora, Y. K., Mathur, R. K., Iqbaluddin, Prasad, B., Sahai, T. N., Sharma, S.B. (1997) *The Precambrian Geology of Aravalli Region, Southern Rajasthan and North Eastern Gujrat, Mem. Geol. Surv. India. Vol 123*, pp 262.
- Hazarika, P., Upadhyay, D., Misra, B. (2013) *Contrasting Geochronological Evolution of the Rajpura-Dariba and Rampura- Agucha Metamorphosed Zn-Pb deposit, Aravalli-Delhi Belt, India. Journal of Asian Earth Sciences*, Vol 73, pp 429-439.
- Heron, A.M. (1953) *The Geology of Central Rajputana Mem. Geol. Surv. India*, Vol 79, pp 389.
- Holler, W., Gandhi, S.M. (1995) *Silver-Bearing Sulfosalt from the Metamorphosed Rampura—Agucha Zn—Pb—(Ag) Deposit, Rajasthan, India. Canadian Mineralogist*, Vol 33, pp 1047—1057.
- Holler, W., Stumpfi, E. F. (1995) *Cr-V Oxides from the Rampura—Agucha Pb—Zn—(Ag) Deposit, Rajasthan, India. Canadian Mineralogist*, Vol 33, pp 745-752.

E: ISSN No. 2349-9443

- Holler, W., Touret, J. L. F., Stumpf, E. F. (1996) *Retrograde Fluid Evolution at Rampura—Agucha Pb-Zn(Ag) Deposit, Rajasthan, India. Mineralium Deposita, Vol 31, pp 163-171.*
- Lyll, K. D., Paterson, M.S. (1966) *Plastic Deformation of Galena (Lead Sulphide). Acta. Metal., Vol 14, pp 371—383.*
- Misra, B, and Bernhardt, H. J. (2009) *Metamorphism, Graphite Crystallinity and Sulfide Anatexis of the Rampura-Agucha massive sulfide deposit, Northwestern India. Mineralium Deposita, Vol 44(2), pp 183*
- Mukherjee, A.D., Guha-Lahiri, S., Bhattacharya, H.N. (1991) *Silver bearing sulfosalts from Rampura—Agucha massive sulphide deposit of Rajasthan. Journal of Geological Society of India, Vol 37, pp 132—135.*
- Raja Rao, C. S. (1970): *Precambrian Sequence of Rajasthan. Misc. Publ. Geol. Surv. India, Vol 23, pp 97—576.*
- Raja Rao, C.S., Poddar, B.C., Chatterjee, A.K. (1976) *Precambrian Stratigraphy of Rajasthan—a Review. Rec. Geol. Surv. India, Vol 101(2), pp 60-79.*
- Ramakrishnan, M., Vaidyanadhan, R., (2008) *Geology of India, Vol.1., Geol. Soc. of India, Bangalore.*
- Ranawat, P.S., Bhatnagar, S.N., Sharma, N.K., (1988) *Metamorphic Character of Rampura—Agucha Pb—Zn deposits, Rajasthan. In Precambrian of the Aravalli Mountain,*

# Asian Resonance

*Rajasthan, India, (ed.), A. B. Roy. Mem. Geol. Soc. India, Vol 7, pp 397—409.*

- Ray, J.N. (1980) *An Evaluation of the Tectonic Framework of the Rampura—Agucha Lead-Zinc Deposit, Bhilwara district, Rajasthan. Indian Minerals, Vol 34, pp 19—21.*
- Roy, A. B., Somani, M. K., Sharma, N. K. (1981) *Aravally—Pre-Aravally Relationship: A Study from the Bhinder Region, Southern Rajasthan. Indian Journal of Earth Sciences, Vol 8, pp 119—130.*
- Sarkar, S. C., Bhattacharya, P. K., Mukherjee, A. D. (1980) *Evolution of the Sulphide Ores of Saladipura, Rajasthan, India, Economic Geology, Vol 75, pp 1152—1167.*
- Shah, N. (2004) *Rampura—Agucha, a remobilised SEDEX deposit, Southeastern Rajasthan, India. In M. Deb and W. D. Goodfellow (Eds), Sediment-hosted lead-zinc sulfide deposits, Narosa, pp 290—303.*
- Sinha-Roy, S. (1984) *Precambrian Crustal Interaction in Rajasthan, NW India. Indian Journal of Earth Sciences, Vol CEISM, pp 84—91.*
- Viswanath, U., Prasad, K.S. and Joshi, A. (2006) *Geo-Metallurgical studies of Rampura- Agucha Deposit. Proceedings of the International seminar on Mineral Processing Technology*
- Vokes, F. M. (1973) *“Ball textures“ in Sulphide Ores. Geol. Foren. Stockholm. Forth. Vol 5, pp 403—406.*

## Figures

**Fig – I : Rampura - Agucha deposit at Rajasthan , India**



# Asian Resonance

Fig- 2: Mineralised Sedimentary Belts within BGC (after Sinha-Roy 1984).

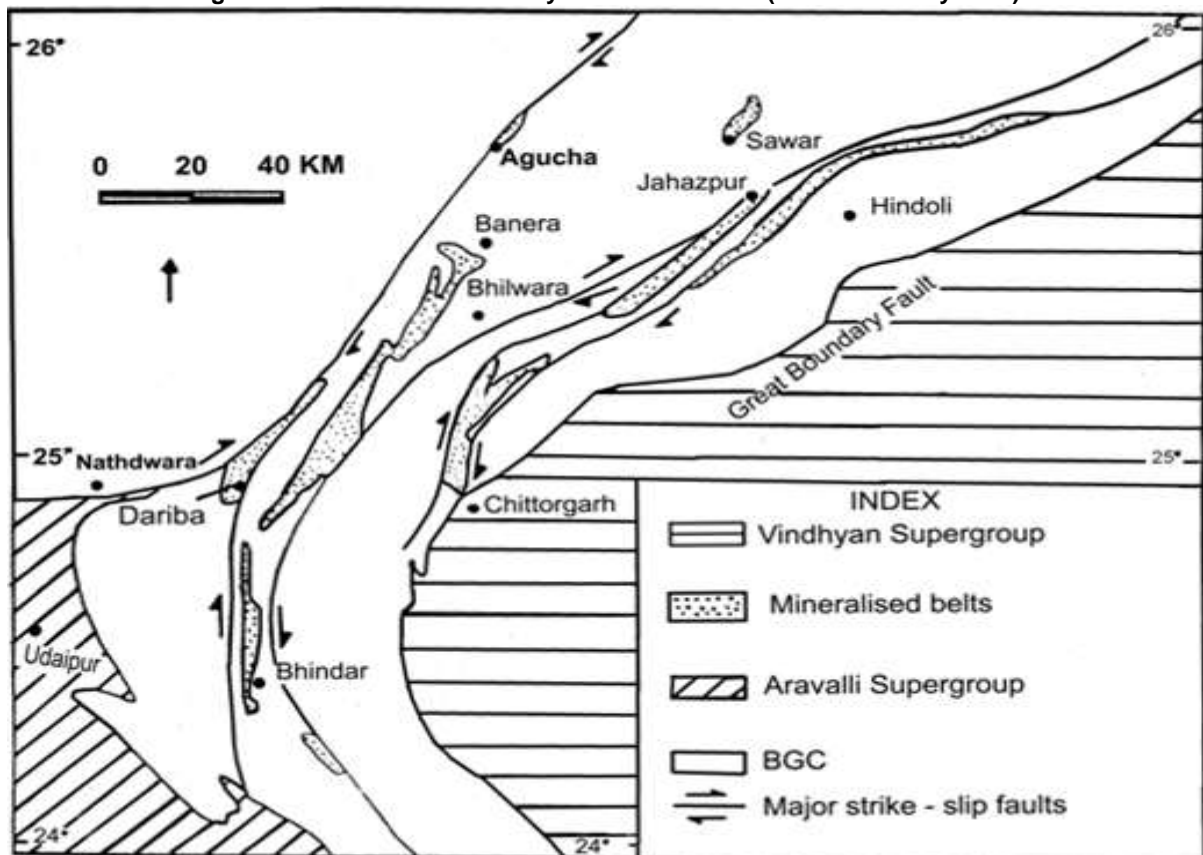


Fig -3 : Geological map showing distribution of Major Stratigraphic Units of the Aravalli craton (modified after Roy and Jakhar, 2002,p.40) A- Alwar ; BI-Bhilwara; BN- Bhindar; BW- Beawar; M- Mangalwar; N- Nathdwara; P- Pisangan; PH- Phuvad; RA- Rampura-Agucha; RD- Rajpura- Dariba; S – Salumar; SR – Sarara; Z – Zawar.

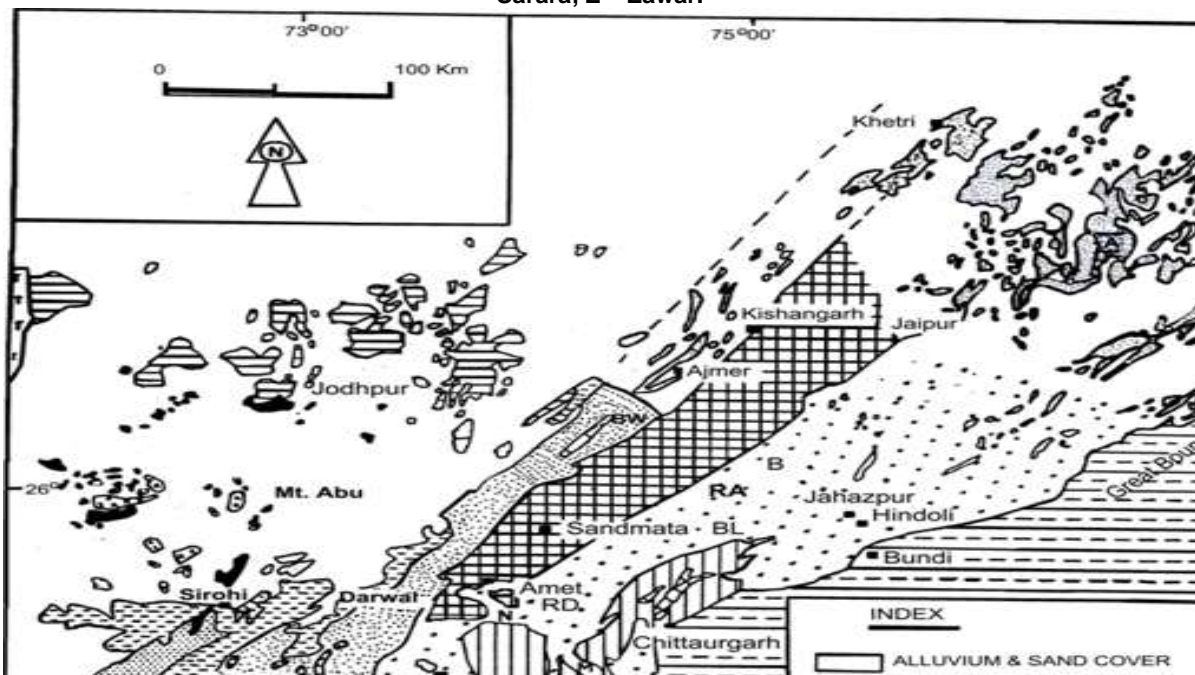


Fig. 4: A Geogological Map of The Rampura- Agucha Area (After Deb And Sehgal, 1997).

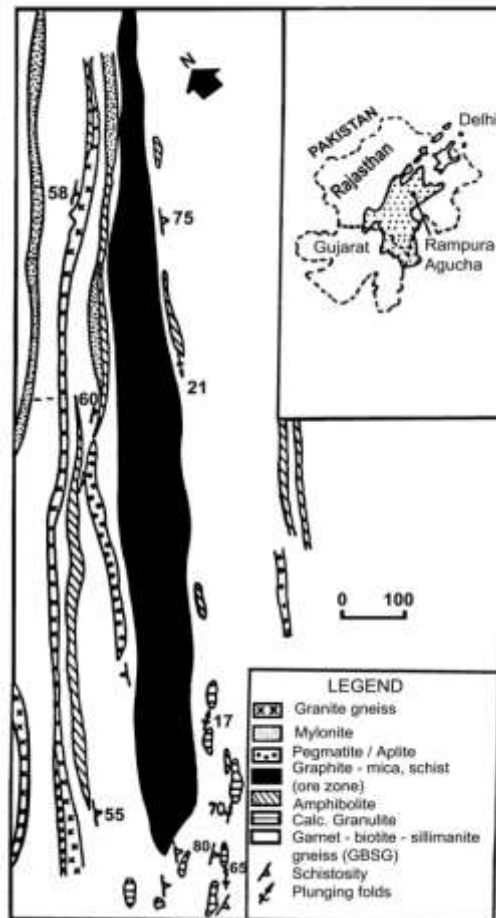


Fig. 5: A Generalized Transverse Section through the Ore Deposit at Rampura-Agucha (After Bhatnagar and Mathur, 1989).

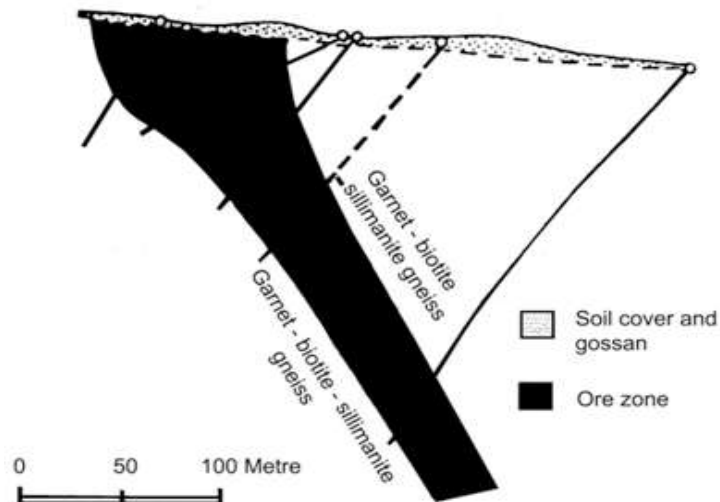


Fig. 6: Rounded Balls of Feldspar-Cordierite Float in Sphalerite (SP) Matrix. (Plane Polarized Light).

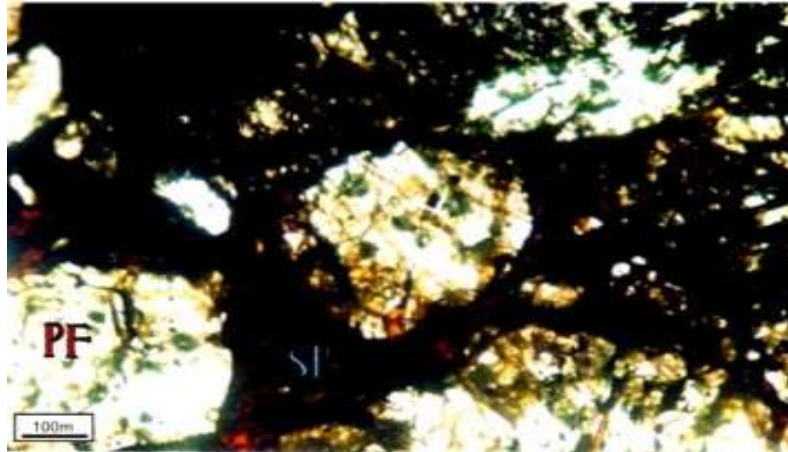


Fig. 7: The Phyllosilicate Grains (Psi) are fragmented and broken apart in sphalerite (SP) matrix. (Plane Polarized light).

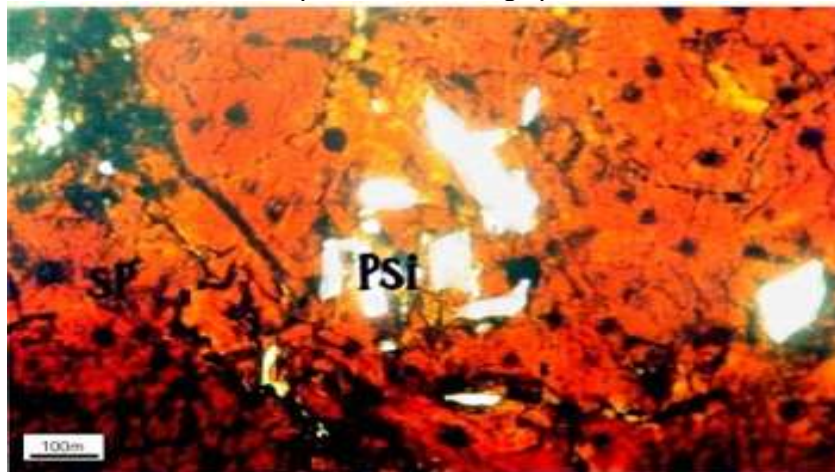


Fig. 8: Elongated Pyrrhotite (Po) Grains Are Oriented within the Sphalerite (Sp) Matrix. (Plane Polarized Light).



Fig. 9: Spherulites of Sphalerite (Sp) Have Protruded the Silicate Aggregates of Plagioclase Feldspar (PF) And Sillimanite(S). No Hydrous Mineral is Found Near by; Is It A Plastic Flowage? (Plane Polarized Light).



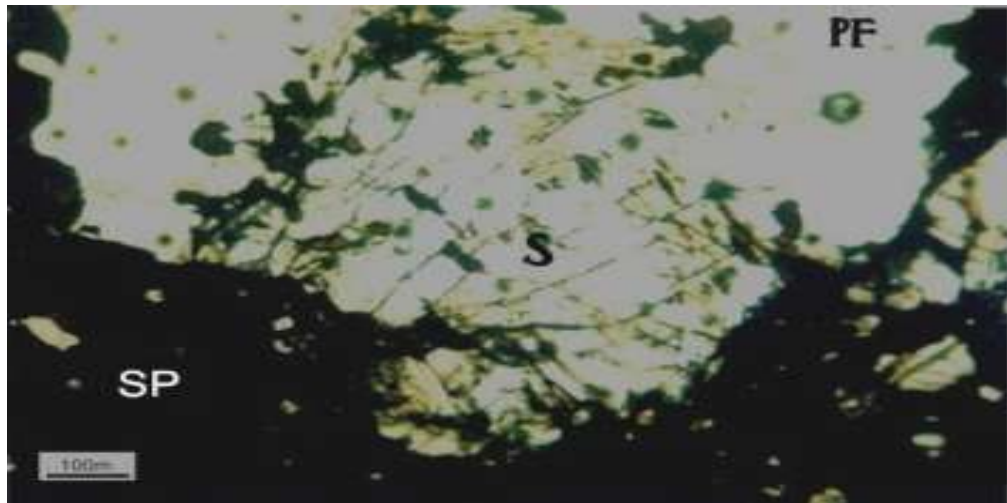


Fig. 10: Granular fabric in Sphalerite (Sp) Aggregate. Grain size varies widely within the limits of a single photomicrograph, apparently constrained by deformation recrystallisation. Grains contain growth and deformation twins. Polygonisation is differential. The section has been etched with saturated chromic acid solution. PO: Pyrrhotite,(Plane Polarized Light).



Fig. 11: A graphite (G) Grain is being kinked within Sphalerite (SP) Matrix. Pyrrhotite (PO) Grains are included in Sphalerite. (Plane Polarized Light).



Fig. 12: Droplets of Pyrrhotite(po) are included within the Quartz-Feldspathic Matrix without any Hydrous Minerals occurring nearby. PF: Plagioclase Feldspar, (Plane Polarized Light).

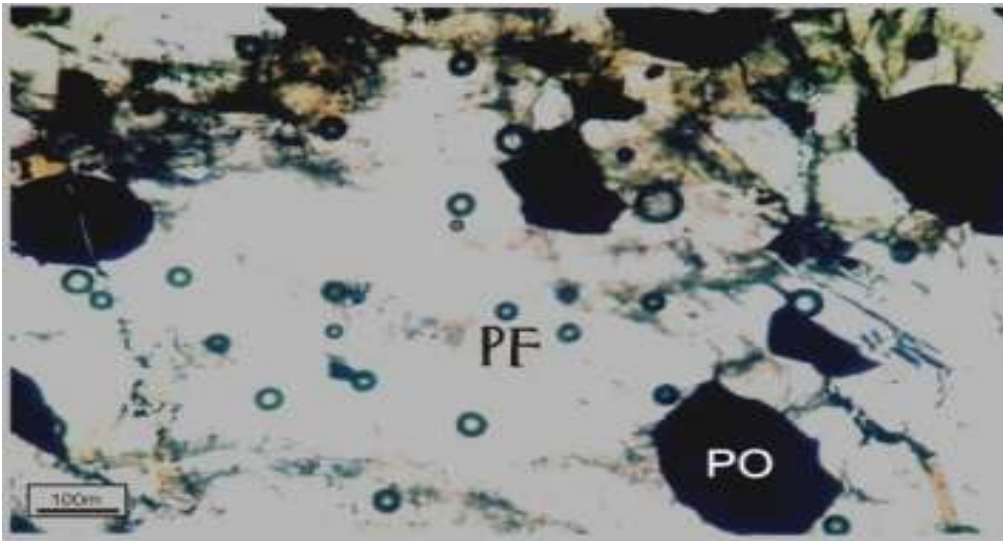


Fig. 13: Grains of Sphalerite (SP) and pyrrhotite (PO) are included within the phyllosilicate (PSi) and are oriented along with the silicate grains parallel to the Foliation. (Plane Polarized Light).

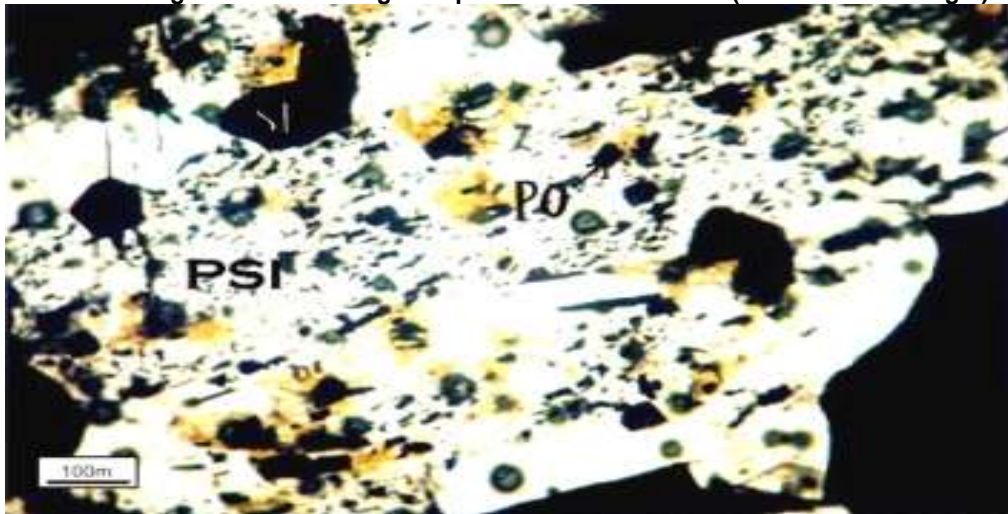


Fig. 14: The Silicate (Si) Grains and Pyrrhotite (Po) grains are Elongated Parallel to the Regional Foliation. (Plane Polarized Light)

